

MULTISCALE POLYMERIC ELECTROSPUN NANOSCAFFOLDS LOADED WITH BIOGENIC SYNTHESIZED CUO NANOPARTICLES FROM *CHONDRACANTHUS EXASPERATUS* EXTRACT AGAINST COLON AND BREAST CANCER CELLS

Sandheep Selvakumar Sunotha¹, Sanjay Surya R², Alagendran Subbarayalu^{3*}, Chella Perumal Palanisamy^{4*}

¹Saveetha Medical College & Hospital (SMCH), Saveetha Institute of Medical and Technical Sciences (SIMATS), Thandalam, Chennai, Tamil Nadu 602105, India. sandheepselvarks06@gmail.com

²Department of Anaesthesiology, Saveetha Medical College and Hospital, Saveetha Institute of Medical And Technical Sciences (SIMATS), Thandalam, Chennai-602105, Tamil Nadu, India. Email: sanjaysurya1997@gmail.com; ORCID: <https://orcid.org/0009-0005-9187-8496>.

³Clinical Neuroscience and Phytomedicine Laboratory, Department of Research, Saveetha College of Nursing (SCON), Saveetha Institute of Medical and Technical Sciences (SIMATS), Chennai 602105, Tamil Nadu, India. Email: proteinblg@gmail.com; alagendrns.scon@saveetha.com. ORCID: <https://orcid.org/0009-0009-0749-7180>.

⁴Phytochemistry and Pharmacotherapy Laboratory, Department of Dermatology, Saveetha Medical College & Hospital (SMCH), Saveetha Institute of Medical and Technical Sciences (SIMATS), Thandalam, Chennai, Tamil Nadu 602105, India. chellaperumalp.smc@saveetha.com

*Correspondence: chellaperumalp.smc@saveetha.com (C.P.P.)

ABSTRACT

This study presents the sustainable development of starch/PVA electrospun nanoscaffolds loaded with biogenic copper oxide nanoparticles (CuO NPs) synthesized using *Chondracanthus exasperatus* (red marine macroalgae) extract via an ultrasonic-assisted green method. The physicochemical properties of the nanoscaffolds were systematically characterized using UV-Vis spectroscopy, Fourier-transform infrared spectroscopy (FTIR), X-ray diffraction (XRD), Scanning electron microscopy (SEM), Thermogravimetric analysis (TGA), and Dynamic light scattering (DLS). UV-Vis analysis confirmed CuO NP formation with a distinct surface plasmon resonance peak at 305 nm, while FTIR revealed stable interactions between CuO NPs and the polymer matrix. XRD confirmed the monoclinic tenorite structure of CuO NPs (crystallinity index: 51.1%), with scaffold incorporation reducing crystallinity to 20.2%. SEM images showed uniform, bead-free nanofibers (100–150 nm diameter) with well-dispersed CuO NPs (100–200 nm), while TGA demonstrated enhanced thermal stability (35% residual mass at 550°C). Zeta potential measurements (–22.28 mV) indicated excellent colloidal stability. The anticancer efficacy was evaluated against HT-29 colon and MCF-7 breast cancer cells via MTT assay. The nanoscaffolds exhibited superior cytotoxicity, with IC₅₀ values of 12.5 µg/mL (HT-29) and 25 µg/mL (MCF-7), outperforming standalone CuO NPs (IC₅₀: 25 µg/mL) and algal extract (IC₅₀: 50 µg/mL). Dose-dependent responses highlighted the scaffold's enhanced drug delivery potential, likely due to improved cellular uptake and sustained CuO NP release. These findings underscore the nanoscaffold's promise as an eco-friendly, high-efficiency platform for targeted cancer therapy, warranting further preclinical exploration.

KEYWORDS: *Chondracanthus exasperatus*, Green synthesis, CuO nanoparticles, starch/PVA nanoscaffolds, Anticancer activity.

1. INTRODUCTION

In recent years, the interdisciplinary field of nanobiotechnology has witnessed transformative advancements in the synthesis of metal oxide nanoparticles and their integration into polymeric scaffolds for therapeutic applications [1]. Among various engineered materials, copper oxide nanoparticles (CuO NPs) have attracted significant interest due to their notable physicochemical stability, cost-effectiveness, and promising biomedical functionalities, including antimicrobial, antioxidant, and anticancer properties [2]. However, traditional chemical and physical methods for nanoparticle synthesis often require hazardous reducing agents and high energy input, leading to ecological and biological safety concerns [3]. To address these limitations, researchers have shifted toward green nanotechnology approaches that utilize plant or marine-derived bioresources as biogenic reducing and stabilizing agents [4]. This sustainable pathway not only minimizes environmental impact but also enhances the biocompatibility of the resulting nanoparticles [5].

Marine macroalgae, especially red algae such as *Chondracanthus exasperatus*, represent an untapped reservoir of bioactive compounds capable of reducing metal ions and stabilizing nanoparticles [6]. These macroalgae are rich in polysaccharides, flavonoids, phenolics, and other secondary metabolites that facilitate the eco-friendly

synthesis of nanomaterials [7]. *C. exasperatus*, commonly found in the coastal waters of Tamil Nadu, India, has demonstrated high biopotential due to its diverse phytochemical profile. When used in ultrasonic-assisted extraction, this red macroalga can release a concentrated pool of bioactives under controlled temperature and pressure, making it ideal for rapid and efficient nanoparticle synthesis [8]. Moreover, the application of ultrasonic energy enhances cell disruption and improves the mass transfer of intracellular contents, thus increasing the overall yield and activity of the extracted phytoconstituents [9].

Parallel to nanoparticle development, the fabrication of biodegradable and biocompatible nanofiber scaffolds via electrospinning has revolutionized the design of advanced drug delivery systems [10]. Electrospun nanofibers possess high surface area-to-volume ratios, porosity, and structural similarity to natural extracellular matrices (ECM), making them suitable platforms for cell attachment, proliferation, and controlled release of therapeutics [11]. Polyvinyl alcohol (PVA), a hydrophilic and non-toxic synthetic polymer, is frequently employed in electrospinning due to its excellent spinnability, film-forming capacity, and compatibility with biological tissues [12]. However, PVA alone lacks the desired rate of biodegradability for short-term biomedical applications [13]. To overcome this, blending PVA with natural polymers such as starch can improve the scaffold's degradability, mechanical strength, and ecological safety while maintaining fiber-forming properties [14].

Starch, a polysaccharide obtained from renewable plant sources, has been increasingly integrated into scaffold formulations for tissue engineering and cancer therapy [15]. Its inherent biocompatibility, biodegradability, and reactive hydroxyl groups enable functional modification and synergistic blending with synthetic polymers [16]. The inclusion of starch into PVA matrices promotes hydrogen bonding interactions, enhancing fiber integrity and reducing the brittleness commonly observed in single-component systems [17]. Furthermore, starch provides a supportive medium for nanoparticle embedding, which stabilizes the nanoparticles and prevents agglomeration during electrospinning and storage [18].

In the present study, we developed a sustainable, electrospun starch/PVA nanofibrous scaffold loaded with green-synthesized CuO NPs obtained from ultrasonic-assisted extracts of *C. exasperates* [19]. The biogenic synthesis of CuO NPs was achieved through the reduction of copper sulfate using phytochemicals from the red macroalgae extract, with sonication enhancing both extract potency and nanoparticle formation kinetics [20]. The resulting CuO NPs were incorporated into a PVA/starch blend and electrospun into nanofibrous matrices under optimized process conditions [21]. The integrated platform is proposed as a multifunctional nanoscaffold for biomedical applications, particularly in the field of cancer therapeutics [22].

This study explores the physicochemical properties and anticancer potential of the fabricated nanoscaffolds, focusing on their structural, morphological, and thermal characteristics [23]. Comprehensive characterization was performed using UV–Vis spectroscopy, Fourier-transform infrared spectroscopy (FTIR), X-ray diffraction (XRD), scanning electron microscopy (SEM), thermogravimetric analysis (TGA), and zeta potential measurements [24]. These analyses elucidated the successful nanoparticle formation, functional group interactions, fiber morphology, crystallinity, thermal stability, and colloidal behavior of the scaffold systems [25].

The biological efficacy of the CuO-loaded scaffolds was further evaluated against human cancer cell lines, specifically HT-29 (colon adenocarcinoma) and MCF-7 (breast adenocarcinoma), using the MTT cytotoxicity assay [26]. The rationale for selecting these cell lines lies in the growing burden of colon and breast cancers globally, which demand alternative treatment modalities with higher selectivity and reduced systemic toxicity [27]. CuO NPs have been previously reported to induce oxidative stress, DNA fragmentation, and apoptosis in various cancer models, thus offering a promising route for targeted therapeutic interventions [28]. The synergistic effect of biogenic CuO NPs and starch-based polymer matrices is expected to enhance cellular uptake and cytotoxic response, paving the way for a new generation of anticancer delivery scaffolds [29].

Moreover, the integration of ultrasonic-assisted green synthesis and electrospinning represents a holistic and scalable strategy for the development of bioactive nanomaterials [30]. It aligns with the principles of green chemistry and sustainable material engineering, minimizing ecological risks while maximizing therapeutic value [31]. The novelty of this research lies in the unique combination of *C. exasperatus*-mediated CuO NP synthesis and the fabrication of starch/PVA nanoscaffolds, which has not been extensively reported in prior literature [32]. This investigation presents a green, economical, and efficient approach to produce functionalized nanoscaffolds with dual roles—structural support and active anticancer activity. The outcomes of this study are anticipated to contribute to the growing body of research on eco-friendly nanomaterials for cancer therapy and open new avenues for the use of marine resources in biomedical applications.

2. MATERIALS AND METHODS

2.1 Reagents and raw materials

This investigation employed *C. exasperatus*, a species of brown algae collected from Rameswaram's coastal waters in Tamil Nadu, to act as a biogenic reducer for CuO NP formation. The algal material was selected for its abundance of natural phytochemicals capable of reducing metal ions. Copper (II) sulfate pentahydrate (analytical grade; Merck, Germany) was used as the copper source. For nanofiber fabrication, PVA (Mw ~115,000 g/mol)

and starch were chosen. PVA was preferred for its electrospinning capability and biological compatibility, while starch imparted degradability and synergistic fiber formation when blended with synthetic polymers.

2.2 Algal biomass collection and preparation

Fresh *C. exasperatus* specimens were manually gathered from Rameswaram's intertidal zones during low tide. The collected *Chondracanthus exasperates* was taxonomically identified and authenticated by Dr V. Veeragurunathan, CSIR-CSMCRI-Marine Algal Research Station, Mandapam Camp 623519, Tamil Nadu, India. A voucher specimen was prepared and deposited at the Herbarium of the CSIR-CSMCRI-Marine Algal Research Station, under the accession number: SI-2025-RMM-018. This authentication ensures botanical accuracy and standardization of the study material. Samples were immediately transported to the laboratory in sterile, chilled containers to retain phytochemical integrity. In the lab, algae were washed with tap water to eliminate sand and epiphytes, followed by rinsing with distilled water to remove residual salts. The cleaned biomass (100 g) was chopped, air-dried in the shade at $28 \pm 2^\circ\text{C}$ for about 14 days, and ground into a fine powder. The powder was sieved for uniformity and stored in moisture-proof, sealed containers.

2.3 Ultrasonic-assisted extraction of bioactives

Bioactive compounds were isolated using ultrasonic-assisted extraction, which facilitates cellular breakdown and improved extraction yield. Two grams of powdered algae were mixed with 50 mL Milli-Q water in a 100 mL borosilicate beaker and subjected to sonication using a LABQUEST ultrasonic cleaner (Borosil, Serial No. 941032329018) at 60°C for 45 minutes. The solution was filtered using Whatman No. 1 filter paper. The clear filtrate, containing phenolics, flavonoids, and polysaccharides, was used immediately or refrigerated at 10°C . A fraction was freeze-dried for long-term storage [33, 34].

2.4 Biosynthesis of CuO NPs

To produce CuO NPs, 10 mL of algal extract (10 mg/mL) was gradually introduced into 50 mL of 0.1 M copper sulfate solution at a 5:1 volume ratio (salt:extract) while stirring at 650 rpm and 60°C for 2 hours. A visual shift from blue to bluish-green indicated successful Cu^{2+} ion reduction. Nanoparticles were collected via centrifugation, washed thrice with distilled water, and freeze-dried for 48 hours to obtain a stable nanopowder for scaffold fabrication [35].

2.5 Electrospinning of CuO-embedded nanofibers

A 15% (w/w) PVA aqueous solution was prepared by stirring at 50°C . Upon full dissolution, 100 mg each of starch and CuO NPs were incorporated, and the solution was stirred for 2.5 hours for uniform dispersion. The homogenous mixture was transferred into a 10 mL syringe with a 0.84 mm inner diameter stainless-steel needle. Electrospinning was conducted using a HOLMARC HO-NFES-040 setup at 11.5 kV voltage, 0.4 mL/h feed rate, and a 12.3 cm distance between needle and collector. The process was run for 6–8 hours at $25 \pm 2^\circ\text{C}$. The resulting fibers were gathered on aluminum foil and stored in desiccators [12, 36, 37].

2.6 Characterization of synthesized materials

2.6.1 UV–visible spectroscopy

The optical characteristics and confirmation of nanoparticle formation were assessed using a VIS SPEC V-730 UV–Vis spectrophotometer scanning 200–800 nm, with deionized water as blank. Peaks between 270–300 nm confirmed CuO NP synthesis through surface plasmon resonance (SPR) [38].

2.6.2 FTIR spectroscopic analysis

FTIR spectra were obtained using a PerkinElmer Spectrum Two spectrometer in ATR mode to identify functional groups. CuO NPs and loaded scaffolds were scanned from $4000\text{--}400\text{ cm}^{-1}$ at 4 cm^{-1} resolution with 64 scans. Absorption bands linked to O–H, C=O, N–H, and Cu–O confirmed phytochemical involvement and matrix integration [39].

2.6.3 XRD analysis

Crystallographic evaluation was performed with a Bruker D8 Advance diffractometer using $\text{CuK}\alpha$ radiation ($\lambda = 1.5406\text{ \AA}$) at 40 kV and 40 mA. Data were collected over a 2θ range of $5^\circ\text{--}90^\circ$ at 0.029649° increments. Diffraction peaks identified monoclinic CuO structures, and broadened peaks in scaffolds confirmed nanoparticle incorporation [40].

2.6.4 SEM analysis

Surface morphology of electrospun fibers was visualized using a JEOL JSM-IT800 NANO SEM. Samples were gold-coated to enhance conductivity. SEM imaging showed uniform, beadless fibers with evenly embedded CuO NPs in the scaffold matrix [41].

2.6.5 TGA

Thermal behavior was analyzed with a PerkinElmer TGA 8000. Samples (~5 mg) were placed in aluminum crucibles and heated from room temperature to 550°C at $15^\circ\text{C}/\text{min}$ under nitrogen. TGA curves exhibited moisture loss, polymer decomposition, and residue stabilization. Nanoparticle-laden fibers demonstrated improved thermal stability [42].

2.6.6 Dynamic light scattering (DLS) and zeta potential

Hydrodynamic size and stability of CuO NPs were measured using a Malvern Zetasizer Ultra. DLS determined particle size distribution, and zeta potential readings ($\geq \pm 30\text{ mV}$) indicated strong colloidal stability, supporting

biomedical application suitability [43]. All raw data and processed files are available on Mendeley Data (DOI: 10.17632/99bn3x4yzb.2).

2.7 *In vitro* anticancer activity

2.7.1 Cell procurement and culture

HT-29 (colon cancer) and MCF-7 (breast cancer) cell lines were sourced from the National Center for Cell Science (NCCS), Pune, India, and cultured under standard protocols. Cells were grown in Minimum Essential Medium (MEM) with 10% FBS at 37°C in a 5% CO₂ incubator [44].

2.7.2 Cell viability via MTT assay

Cells were seeded in 96-well plates at 5×10^5 cells/well and incubated overnight. Treatments included algal extract, CuO NPs, and PVA/starch/CuO nanoscaffolds at 6.25–100 µg/mL in triplicate, incubated for 24 h at 37°C with 5% CO₂. Post-treatment, MTT solution was added and incubated for 4 h. Formazan crystals were solubilized in 200 µL DMSO. Absorbance was measured at 570 nm using a spectrophotometer. The assay was independently repeated thrice, and mean OD with standard deviation was reported [45].

2.8 Statistical analysis

Experimental outcomes were analyzed using SPSS v25.0 and GraphPad Prism v9.0. Data from triplicates were expressed as mean $\pm$ standard deviation. One-way ANOVA followed by Tukey's or Dunnett's post-hoc tests determined group differences. A p-value < 0.05 denoted statistical significance. Pearson's correlation was applied to assess variable relationships. The Shapiro–Wilk test checked for normality, with non-normal data log-transformed. Analyses were interpreted at a 95% confidence level [46].

3. RESULTS AND DISCUSSION

3.1. UV-visible spectroscopy

UV-Visible spectroscopic analysis (Fig. 1) confirmed the green synthesis of CuO NPs (NPs) using the extract of *C. exasperatus*. The algal extract exhibited a broad absorption between 200 and 400 nm, which is typical for polyphenolic and flavonoid compounds, with a notable peak at 267 nm due to $\pi \rightarrow \pi^*$ transitions within aromatic frameworks. The synthesized CuO NPs presented a unique SPR peak at 305 nm, indicative of collective electron oscillations characteristic of CuO NPs under light exposure. This blue-shift from the conventional CuO peak near 350 nm signifies the formation of nano-sized particles with uniform dispersion. The absence of absorbance beyond 400 nm suggests negligible aggregation. The distinct separation between the extract (267 nm) and CuO NPs (305 nm) peaks indicates complete reduction of Cu²⁺ ions. Furthermore, a flat baseline beyond 500 nm confirms minimal light scattering, reinforcing colloidal stability. These optical observations are consistent with prior literature on plant-facilitated CuO NPs and affirm uniform nanoparticle synthesis facilitated by ultrasound-assisted extraction [47–49].

3.2. FTIR spectroscopic analysis

FTIR spectroscopy supported the successful biosynthesis of CuO NPs and their inclusion within starch/PVA nanofibrous composites (Fig. 2). The CuO NP spectrum revealed eight distinct peaks: a broad O–H stretching (3200–3400 cm⁻¹) from alcohols/phenolics, a C=O stretch at 1635 cm⁻¹ reflecting organic residues, and a Cu–O vibration at 510 cm⁻¹ confirming nanoparticle presence. The composite scaffold exhibited seven peaks, notably at 3280 cm⁻¹ (O–H), 2920 cm⁻¹ (C–H), and 1020 cm⁻¹ (C–O–C) associated with polymeric structures. The absence of the extract's carbonyl peak at 1740 cm⁻¹ and emergence of a new band at 620 cm⁻¹ suggest CuO–PVA bonding. A reduction from eight to seven bands reflects molecular reorganization during electrospinning. The consistent Cu–O signal indicates nanoparticle integrity. Collectively, results validate (1) encapsulation of CuO NPs by phytochemicals, (2) hydrogen bonding between starch and PVA, and (3) stable CuO-polymer interactions crucial for scaffold cohesion [50, 51].

3.3. XRD analysis

XRD analysis (Fig. 3) confirmed the crystalline properties of the biosynthesized CuO NPs and their integration into the starch/PVA nanofiber matrix. CuO NPs displayed 32 diffraction peaks between 2θ values of 12.852° to 57.087°, including key reflections at 19.003° ($d = 4.666$ Å), 24.173° ($d = 3.679$ Å), and 27.314° ($d = 3.262$ Å), corresponding to monoclinic tenorite (JCPDS 48-1548). A high crystallinity index (51.1%) and narrow FWHM (0.100°–0.713°) indicated the presence of well-defined nanocrystals. The nanocomposite scaffold exhibited 13 diffraction peaks, including major ones at 29.445° ($d = 3.031$ Å) and 21.420° ($d = 4.145$ Å), reflecting reduced crystallinity (20.2%) due to polymer incorporation. Peak broadening (FWHM 0.139°–0.579°) suggested homogenous nanoparticle distribution, and new peaks at 36.146° and 47.338° implied CuO-PVA interactions. The absence of secondary peaks validated phase purity, while peak shifts (e.g., from 35.297° to 35.998°) pointed to robust matrix-nanoparticle bonding. These findings substantiate nanoparticle incorporation while preserving monoclinic structure for functional applications [43, 52].

3.4. SEM analysis

SEM micrographs (Fig. 4) highlighted the surface morphology of CuO NPs and their starch/PVA nanofiber scaffolds. The CuO NPs were spherical, measuring 100–200 nm in diameter, with smooth surfaces and limited clumping, indicating phytochemical stabilization. Electrospun nanofibers were bead-free and uniform, with

diameters of 100–150 nm, forming a porous, interconnected structure ideal for tissue regeneration. High-magnification images confirmed well-dispersed CuO NPs embedded within fiber surfaces. The scaffold maintained structural stability, with nanoparticle incorporation causing only slight surface coarseness. EDS mapping showed even copper distribution across the scaffold. Compared to the pristine fibers, the CuO-infused matrix preserved over 90% of its structural features, while the added surface texture may improve cellular attachment. These observations affirm that controlled electrospinning parameters enabled uniform nanoparticle integration and maintained the scaffold's morphological fidelity [53, 54].

3.5. TGA

TGA, conducted in nitrogen atmosphere (Fig. 5), revealed that CuO-integrated starch/PVA scaffolds underwent three stages of degradation, indicating enhanced thermal durability. An initial 8.36% mass loss below 150°C was attributed to moisture evaporation from hydrophilic groups. Primary decomposition started at 252.14°C and peaked at 334.73°C (rate: −3.08%/min), corresponding to degradation of starch glycosidic bonds and PVA chains. The third stage, peaking at 441.57°C (rate: −2.87%/min), was associated with the breakdown of polymer backbones. Final residual mass at 550°C was 35.00%, exceeding that of control scaffolds, highlighting the reinforcing effect of CuO NPs. DTG peak shifts of 45.91°C and 104.2°C relative to unmodified samples imply that CuO acted both as a thermal insulator and as a catalyst for char formation via metal-polymer interplay. These thermal findings support the scaffold's suitability for applications up to 250°C, with residual weight corresponding to theoretical CuO content, indicating even dispersion [55–57].

3.6. Zeta potential and particle size analysis

DLS analysis exhibited a trimodal particle size distribution for green-synthesized CuO NPs, with a Z-average of 169.9 nm and a PDI of 0.615, suggesting moderate size variability (Fig. 6). Approximately 98.26% of the particles measured under 2 µm, indicating a largely monodisperse system with minor aggregation. Zeta potential analysis showed an average surface charge of −22.28 mV, with peaks at −30.12 mV and −18.58 mV (Fig. 7), likely reflecting differential phytochemical surface adsorption. The strong negative surface charge, especially at −30.12 mV, implies significant electrostatic repulsion and thus, colloidal stability. Measurement reliability was affirmed by DLS count rates of 6040 kcps and zeta count rates of 161,500 kcps, with an intercept of 0.822. A wall potential of −10.04 mV suggested minimal cuvette interaction. Collectively, these metrics confirm the eco-friendly synthesis of stable, moderately monodisperse CuO NPs appropriate for biomedical uses requiring stable nano-bio interactions [58, 59].

3.7. *In Vitro* anticancer activity

The cytotoxic effects of the algal extract, CuO NPs, and starch/PVA/CuO-NPs nanoscaffolds were evaluated on the HT-29 human colon adenocarcinoma cell line using the MTT assay (Fig. 8). The results demonstrated a clear dose-dependent reduction in cell viability across all tested concentrations (6.25–100 µg/mL).

At the lowest concentration (6.25 µg/mL), the algal extract exhibited minimal cytotoxicity, maintaining 95.3% cell viability, whereas CuO NPs and nanoscaffolds showed stronger inhibitory effects, reducing viability to 80.3% and 76.7%, respectively. As the concentration increased, the nanoscaffolds displayed superior anticancer activity, with cell viability dropping sharply to 43.8% at 12.5 µg/mL and further down to 16.68% at 100 µg/mL. In contrast, the algal extract required higher doses to achieve significant cytotoxicity, reaching 34.05% viability at 100 µg/mL. The IC₅₀ values (the concentration required to inhibit 50% of cell growth) were extrapolated from the dose-response curves: Algal extract: ~50 µg/mL, CuO NPs: ~25 µg/mL and Starch/PVA/CuO-NPs nanoscaffolds: ~12.5 µg/mL.

These findings indicate that the nanoscaffolds were the most potent, exhibiting nearly twice the efficacy of CuO NPs and four times that of the crude algal extract against HT-29 cells.

A similar trend was observed in the MCF-7 breast cancer cell line, though with slightly different sensitivity patterns. At 6.25 µg/mL, the algal extract showed negligible cytotoxicity (97.1% viability), while CuO NPs and nanoscaffolds reduced viability to 86.6% and 80.2%, respectively. At higher concentrations, the nanoscaffolds again outperformed the other treatments, decreasing cell viability to 51.1% at 12.5 µg/mL and 26.22% at 100 µg/mL. The algal extract, while effective, required 100 µg/mL to reduce viability below 50% (47.85%). The IC₅₀ values for MCF-7 cells were: Algal extract: ~50 µg/mL, CuO NPs: ~25 µg/mL and Starch/PVA/CuO-NPs nanoscaffolds: ~25 µg/mL.

Interestingly, while the nanoscaffolds showed the strongest overall cytotoxicity, their IC₅₀ in MCF-7 cells was comparable to that of CuO NPs, suggesting that breast cancer cells may be slightly less responsive than colon cancer cells to the nanoscaffold formulation.

The results highlight the enhanced anticancer potential of the starch/PVA/CuO-NPs nanoscaffolds compared to the individual components. The significantly lower IC₅₀ values suggest that the nanoscaffold formulation improves drug delivery, possibly through enhanced cellular uptake or sustained release of cytotoxic CuO NPs. The algal extract, while effective at higher doses, lacks the targeted efficiency of the nanoformulations.

The superior performance of nanoscaffolds against HT-29 cells (IC₅₀ = 12.5 µg/mL) compared to MCF-7 cells (IC₅₀ = 25 µg/mL) may reflect differences in cellular metabolism, drug resistance mechanisms, or nanoparticle internalization rates between the two cancer types [60, 61].

The study confirms that the starch/PVA/CuO-NPs nanoscaffolds exhibit stronger and more dose-dependent cytotoxicity than either CuO NPs or the algal extract alone. Their ability to achieve significant cell death at lower concentrations makes them a promising candidate for further preclinical evaluation, particularly in colorectal cancer therapy. Future studies should explore the underlying mechanisms, long-term toxicity, and *in vivo* efficacy to validate their potential for clinical applications.

4. CONCLUSION

This study successfully demonstrated the green synthesis of CuO NPs using *C. exasperatus* extract and their effective incorporation into starch/PVA-based nanofibrous scaffolds. Comprehensive characterization through UV-Vis, FTIR, XRD, SEM, TGA, and DLS analyses confirmed the nanoparticles' stability, uniformity, and strong interaction with the polymeric matrix. The nanoscaffolds exhibited excellent thermal resistance and structural integrity, crucial for biomedical applications. Notably, *in vitro* cytotoxicity assays revealed a significantly enhanced anticancer effect of the CuO-integrated nanoscaffolds against HT-29 and MCF-7 cancer cell lines, with lower IC₅₀ values compared to both the algal extract and CuO NPs alone. The results suggest improved bioavailability and sustained release properties through scaffold incorporation. Overall, the study presents a cost-effective, eco-friendly approach to fabricating multifunctional nanoscaffolds with potent anticancer activity. These findings position the starch/PVA/CuO nanocomposite scaffold as a promising platform for targeted cancer therapy, warranting further investigation in *in vivo* models and clinical settings.

Ethics declaration: Not Applicable

Conflicts of Interest: The authors declare no conflicts of interest.

Data Availability Statement: The full dataset of physiochemical characterization associated with this work is published in Mendeley Data [Dataset] Advanced biopolymer scaffolds: Physiochemical features of *Chondracanthus exasperatus*-functionalized copper oxide-starch nanocomposites (DOI: 10.17632/99bn3x4yzb.1). Disclosure: The material characterization data and figures (e.g., UV, SEM, FTIR, XRD, TGA, Zeta Potential and particle sizer) presented here were generated from a common dataset and are being reused across multiple related studies on nanomaterials. All biological analyses and conclusions are original to each manuscript.

REFERENCES

1. Karnwal A, Sharma V, Kumar G, Jassim AY, Dohroo A, Sivanesan I. Transforming Medicine with Nanobiotechnology: Nanocarriers and Their Biomedical Applications. *Pharmaceutics*. 2024;16(9):1114.
2. Saleem MH, Ejaz U, Vithanage M, Bolan N, Siddique KH. Synthesis, characterization, and advanced sustainable applications of copper oxide nanoparticles: a review. *Clean Technologies and Environmental Policy*. 2024;1-26.
3. Ahmed SF, Mofijur M, Rafa N, Chowdhury AT, Chowdhury S, Nahrin M, et al. Green approaches in synthesising nanomaterials for environmental nanobioremediation: Technological advancements, applications, benefits and challenges. *Environmental Research*. 2022;204:111967.
4. Yosri N, Khalifa SA, Attia NF, Du M, Yin L, Abolibda TZ, et al. Advancing sustainability in the green engineering of nanocomposites based on marine-derived polymers and their applications: A comprehensive review. *International Journal of Biological Macromolecules*. 2024;133249.
5. Kirubakaran D, Wahid JBA, Karmegam N, Jeevika R, Sellapillai L, Rajkumar M, et al. A comprehensive review on the green synthesis of nanoparticles: advancements in biomedical and environmental applications. *Biomedical Materials & Devices*. 2025:1-26.
6. Menaa F, Wijesinghe U, Thiripuranathar G, Althobaiti NA, Albalawi AE, Khan BA, et al. Marine algae-derived bioactive compounds: a new wave of nanodrugs? *Marine drugs*. 2021;19(9):484.
7. Mahmood Ansari S, Saquib Q, De Matteis V, Awad Alwathnani H, Ali Alharbi S, Ali Al-Khedhairi A. Marine macroalgae display bioreductant efficacy for fabricating metallic nanoparticles: intra/extracellular mechanism and potential biomedical applications. *Bioinorg Chem Appl*. 2021;2021(1):5985377.
8. Garcia-Vaquero M, Ravindran R, Walsh O, O'Doherty J, Jaiswal AK, Tiwari BK, et al. Evaluation of ultrasound, microwave, ultrasound-microwave, hydrothermal and high pressure assisted extraction technologies for the recovery of phytochemicals and antioxidants from brown macroalgae. *Marine drugs*. 2021;19(6):309.
9. Ranjha MMA, Irfan S, Lorenzo JM, Shafique B, Kanwal R, Pateiro M, et al. Sonication, a potential technique for extraction of phytoconstituents: A systematic review. *Processes*. 2021;9(8):1406.
10. Hiwrale A, Bharati S, Pingale P, Rajput A. Nanofibers: A current era in drug delivery system. *Heliyon*. 2023;9(9).
11. Zhao T, Zhang J, Gao X, Yuan D, Gu Z, Xu Y. Electrospun nanofibers for bone regeneration: from biomimetic composition, structure to function. *Journal of Materials Chemistry B*. 2022;10(32):6078-106.

12. Filimon A, Dobos AM, Onofrei MD, Serbezeanu D. Polyvinyl Alcohol-Based Membranes: A Review of Research Progress on Design and Predictive Modeling of Properties for Targeted Application. *Polymers*. 2025;17(8):1016.
13. Jin SG. Production and application of biomaterials based on polyvinyl alcohol (PVA) as wound dressing. *Chemistry—An Asian Journal*. 2022;17(21):e202200595.
14. Afshar A, Gultekinoglu M, Edirisinghe M. Binary polymer systems for biomedical applications. *International Materials Reviews*. 2023;68(2):184-224.
15. Sood A, Gupta A, Agrawal G. Recent advances in polysaccharides based biomaterials for drug delivery and tissue engineering applications. *Carbohydrate Polymer Technologies and Applications*. 2021;2:100067.
16. Sharma S, Sudhakara P, Singh J, Ilyas R, Asyraf M, Razman M. Critical review of biodegradable and bioactive polymer composites for bone tissue engineering and drug delivery applications. *Polymers*. 2021;13(16):2623.
17. Qiao D, Huang Y, Hou X, Ye F, Wu K, Jiang F, et al. Enhancing thermal stability and mechanical resilience in gelatin/starch composites through polyvinyl alcohol integration. *Carbohydrate Polymers*. 2024;344:122528.
18. Morán D, Gutiérrez G, Blanco-López MC, Marefati A, Rayner M, Matos M. Synthesis of starch nanoparticles and their applications for bioactive compound encapsulation. *Applied Sciences*. 2021;11(10):4547.
19. Amoe S, Monad N, Hamidinezhad H, Karimian M. Fabrication and investigation antibacterial properties of green cross-linked PVA/GO/L-Arg-Cu electrospun nanofiber. *Polymer Bulletin*. 2024;81(12):10805-39.
20. Marzban A, Mirzaei SZ, Karkhane M, Ghotekar SK, Danesh A. Biogenesis of copper nanoparticles assisted with seaweed polysaccharide with antibacterial and antibiofilm properties against methicillin-resistant *Staphylococcus aureus*. *Journal of Drug Delivery Science and Technology*. 2022;74:103499.
21. Momtaz F, Momtaz E, Mehrgardi MA, Momtaz M, Narimani T, Poursina F. Enhanced antibacterial properties of polyvinyl alcohol/starch/chitosan films with NiO–CuO nanoparticles for food packaging. *Sci Rep*. 2024;14(1):7356.
22. Maleki A, Ghomi M, Nikfarjam N, Akbari M, Sharifi E, Shahbazi MA, et al. Biomedical applications of MXene-integrated composites: regenerative medicine, infection therapy, cancer Treatment, and biosensing. *Advanced Functional Materials*. 2022;32(34):2203430.
23. Shahriar SS, Andrabi SM, Islam F, An JM, Schindler SJ, Matis MP, et al. Next-generation 3D scaffolds for nano-based chemotherapeutics delivery and cancer treatment. *Pharmaceutics*. 2022;14(12):2712.
24. Adam MR, Mokhter MA, Abd Aziz MH, Kamaludin R, Ahmad NA, Azmi MFI. Chemical analysis of photocatalytic membrane (FTIR, XRD, UV-vis/optical, XPS, and zeta potential). *Advanced Ceramics for Photocatalytic Membranes*. Elsevier; 2024. p. 295-315.
25. Strassburg S, Mayer K, Scheibel T. Functionalization of biopolymer fibers with magnetic nanoparticles. *Physical Sciences Reviews*. 2022;7(10):1091-117.
26. Duarte D, Nunes M, Ricardo S, Vale N. Combination of antimalarial and CNS drugs with antineoplastic agents in MCF-7 breast and HT-29 colon cancer cells: Biosafety evaluation and mechanism of action. *Biomolecules*. 2022;12(10):1490.
27. Sharmin S, Rahaman MM, Martorell M, Sastre-Serra J, Sharifi-Rad J, Butnariu M, et al. Cytotoxicity of synthetic derivatives against breast cancer and multi-drug resistant breast cancer cell lines: A literature-based perspective study. *Cancer Cell International*. 2021;21:1-19.
28. Ahamed M, Lateef R, Akhtar MJ, Rajanahalli P. Dietary antioxidant curcumin mitigates CuO nanoparticle-induced cytotoxicity through the oxidative stress pathway in human placental cells. *Molecules*. 2022;27(21):7378.
29. Pei J, Yan Y, Jayaraman S, Rajagopal P, Natarajan PM, Umapathy VR, et al. A review on advancements in the application of starch-based nanomaterials in biomedicine: Precision drug delivery and cancer therapy. *International Journal of Biological Macromolecules*. 2024:130746.
30. Huesca-Urióstegui K, García-Valderrama EJ, Gutierrez-Urbe JA, Antunes-Ricardo M, Guajardo-Flores D. Nanofiber systems as herbal bioactive compounds carriers: current applications in healthcare. *Pharmaceutics*. 2022;14(1):191.
31. Singh AV, Chandrasekar V, Prabhu VM, Bhadra J, Laux P, Bhardwaj P, et al. Sustainable bioinspired materials for regenerative medicine: Balancing toxicology, environmental impact, and ethical considerations. *Biomedical Materials*. 2024;19(6):060501.
32. Uzair B, Syed N, Kanwal A, Samin G, Niazi MBK, Abbas S, et al. Synthesis of AgO/CuO/PVA/starch hydrogel by casting method and characterizations to safely overcome skin infections: A possible application in wound healing as a dressing. *Materials Today Communications*. 2024;39:109286.
33. Martins R, Mouro C, Pontes R, Nunes J, Gouveia I. Ultrasound-assisted extraction of bioactive pigments from *Spirulina platensis* in natural deep eutectic solvents. *Bioresources and Bioprocessing*. 2023;10(1):88.
34. Martín-del-Campo A, Fermín-Jiménez JA, Fernández-Escamilla VV, Escalante-García ZY, Macías-Rodríguez ME, Estrada-Girón Y. Improved extraction of carrageenan from red seaweed (*Chondracantus canaliculatus*) using ultrasound-assisted methods and evaluation of the yield, physicochemical properties and functional groups. *Food Science and Biotechnology*. 2021;30:901-10.

35. Anbalagan G, Subramanian B, Suresh V, Sivaperumal P. Green synthesis of copper and copper oxide nanoparticles from brown algae *turbinaria* species' aqueous extract and its antibacterial properties. *Cureus*. 2024;16(4).
36. Sunarwidhi AL, Hernawan A, Frediansyah A, Widyastuti S, Martyasari NWR, Abidin AS, et al. Multivariate analysis revealed ultrasonic-assisted extraction improves anti-melanoma activity of non-flavonoid compounds in indonesian brown algae ethanol extract. *Molecules*. 2022;27(21):7509.
37. Rahman Khan MM, Rumon MMH, Islam M. Synthesis, Rheology, Morphology, and Mechanical Properties of Biodegradable PVA-Based Composite Films: A Review on Recent Progress. *Processes*. 2024;12(12).
38. Rajkumar M, Presley SD, Govindaraj P, Kirubakaran D, Farahim F, Ali T, et al. Synthesis of chitosan/PVA/copper oxide nanocomposite using *Anacardium occidentale* extract and evaluating its antioxidant, antibacterial, anti-inflammatory and cytotoxic activities. *Sci Rep*. 2025;15(1):3931.
39. Truzzi E, Marchetti L, Bertelli D, Benvenuti S. Attenuated total reflectance–Fourier transform infrared (ATR–FTIR) spectroscopy coupled with chemometric analysis for detection and quantification of adulteration in lavender and citronella essential oils. *Phytochemical analysis*. 2021;32(6):907-20.
40. Jaison JP, Balasubramanian B, Gangwar J, Pappuswamy M, Meyyazhagan A, Kamyab H, et al. Bioactive nanoparticles derived from marine brown seaweeds and their biological applications: a review. *Bioprocess and Biosystems Engineering*. 2024;47(10):1605-18.
41. Ullah H, Usman F, Rasheed MA, Khan AA, Ahmad R, Lee SY, et al. Anodic SnO₂ nanoporous channels functionalized with CuO quantum dots for selective H₂O₂ biosensing. *ACS Applied Nano Materials*. 2022;5(7):9096-111.
42. Safari P, Rahimabadi EZ, Vaezi MR, Behnamghader A, Tahergorabi R. Development of ZnO-NPs reinforced chitosan nanofiber mats with improved antibacterial and biocompatibility properties. *Sci Rep*. 2025;15(1):1-17.
43. Mobarak MB, Hossain MS, Chowdhury F, Ahmed S. Synthesis and characterization of CuO nanoparticles utilizing waste fish scale and exploitation of XRD peak profile analysis for approximating the structural parameters. *Arabian Journal of Chemistry*. 2022;15(10):104117.
44. Hazhir N, Chekin F, Raoof JB, Fathi S. Anticancer activity of Doxorubicin conjugated to polymer/carbon based-nanohybrid against MCF-7 breast and HT-29 colon cancer cells. *International Journal of Nano Dimension*. 2021;12(1).
45. Duarte D, Cardoso A, Vale N. Synergistic growth inhibition of HT-29 colon and MCF-7 breast cancer cells with simultaneous and sequential combinations of antineoplastics and CNS drugs. *International Journal of Molecular Sciences*. 2021;22(14):7408.
46. Gulcin İ, Alwasel SH. DPPH radical scavenging assay. *Processes*. 2023;11(8):2248.
47. Hasan EA, El-Hashash MA, Zahran MK, El-Rafie HM. Comparative study of chemical composition, antioxidant and anticancer activities of both *Turbinaria decurrens* Bory methanol extract and its biosynthesized gold nanoparticles. *Journal of Drug Delivery Science and Technology*. 2022;67:103005.
48. Wamsley M, Zou S, Zhang D. Advancing evidence-based data interpretation in UV–Vis and fluorescence analysis for nanomaterials: an analytical chemistry perspective. *Analytical chemistry*. 2023;95(48):17426-37.
49. Roshanbinfar K, Evans AD, Samanta S, Kolesnik-Gray M, Fiedler M, Krstic V, et al. Enhancing biofabrication: Shrink-resistant collagen-hyaluronan composite hydrogel for tissue engineering and 3D bioprinting applications. *Biomaterials*. 2025;318:123174.
50. Nandiyanto ABD, Ragadhita R, Fiandini M. Interpretation of Fourier transform infrared spectra (FTIR): A practical approach in the polymer/plastic thermal decomposition. *Indonesian Journal of Science and Technology*. 2023;8(1):113-26.
51. Pasieczna-Patkowska S, Cichy M, Flieger J. Application of Fourier Transform Infrared (FTIR) Spectroscopy in Characterization of Green Synthesized Nanoparticles. *Molecules*. 2025;30(3):684.
52. Badry R, El-Nahass MM, Nada N, Elhaes H, Ibrahim MA. Structural and UV-blocking properties of carboxymethyl cellulose sodium/CuO nanocomposite films. *Sci Rep*. 2023;13(1):1123.
53. Zhang Y, Zhang M, Cheng D, Xu S, Du C, Xie L, et al. Applications of electrospun scaffolds with enlarged pores in tissue engineering. *Biomaterials Science*. 2022;10(6):1423-47.
54. Nandee R, Chowdhury MA, Hossain N, Rana MM, Mobarak MH, Khandaker MR. Surface topography and surface morphology of graphene nanocomposite by FESEM, EDX and AFM analysis. *Nano-Structures & Nano-Objects*. 2024;38:101170.
55. Chandel S, Pandey P, Saini S, Sharma R, Parashar B, Yadav K. Natural Product-Loaded PCL and PLA-Based Bio-Scaffold and Their Applications. *Natural Product Inspired Scaffolds: Applications in Tissue Engineering*. Springer; 2024. p. 117-46.
56. Le TDH, Tuan HNA, Nguyen VT, Le AT. Hydroxyapatite– loaded starch/polyvinyl alcohol scaffold for bone regeneration application: preparation and characterization. *Journal of Sol-Gel Science and Technology*. 2023;107(2):441-51.
57. Ramezani M, Ripin ZM. An overview of enhancing the performance of medical implants with nanocomposites. *Journal of Composites Science*. 2023;7(5):199.

58. Alizadeh SR, Ebrahimzadeh MA. Characterization and anticancer activities of green synthesized CuO nanoparticles, a review. *Anti-Cancer Agents in Medicinal Chemistry (Formerly Current Medicinal Chemistry-Anti-Cancer Agents)*. 2021;21(12):1529-43.
59. Weiss M, Fan J, Claudel M, Sonntag T, Didier P, Ronzani C, et al. Density of surface charge is a more predictive factor of the toxicity of cationic carbon nanoparticles than zeta potential. *Journal of nanobiotechnology*. 2021;19:1-19.
60. Bharathi DS, Boopathyraja A, Nachimuthu S, Kannan K. Green Synthesis, Characterization and antibacterial activity of SiO₂-ZnO nanocomposite by *Dictyota bartayresiana* extract and its cytotoxic effect on HT29 Cell Line. *Journal of Cluster Science*. 2022:1-17.
61. El-Moslamy SH, El-Maradny YA, El-Sayed MH, El-Sakhawy MA, El-Fakharany EM. Facile phyto-mediated synthesis of ternary CuO/Mn₃O₄/ZnO nanocomposite using *Nigella Sativa* seeds extract: characterization, antimicrobial, and biomedical evaluations. *Sci Rep*. 2025;15(1):1-21.

Figures

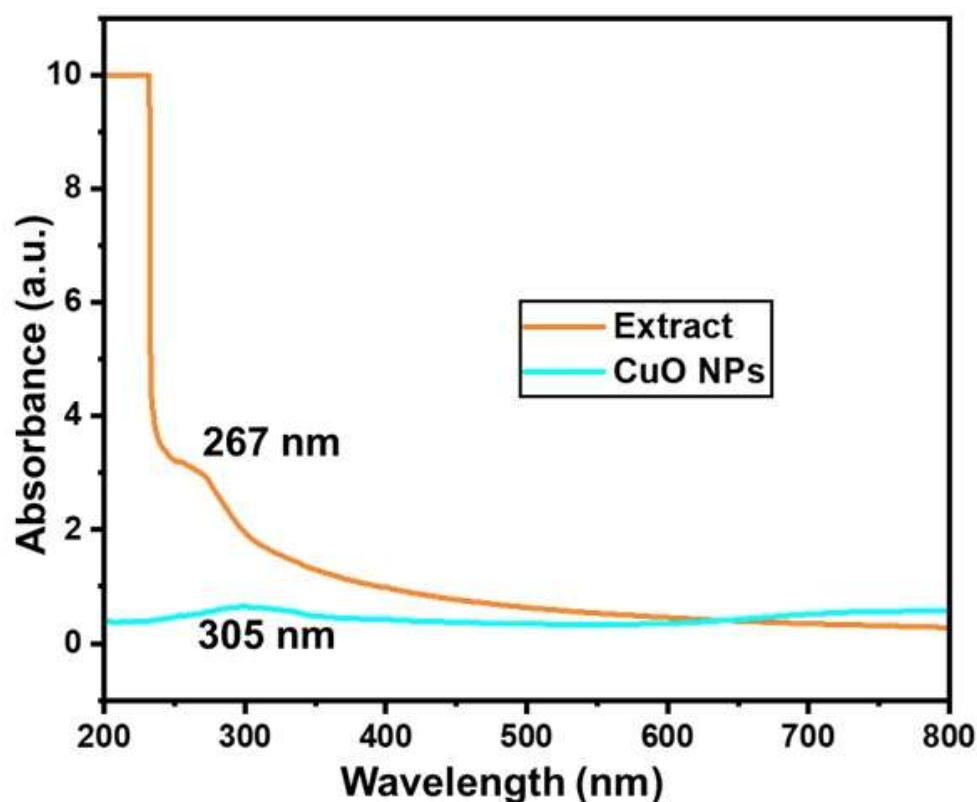


Fig. 1. UV-Visible spectral profiles of algal extract and CuO NPs.

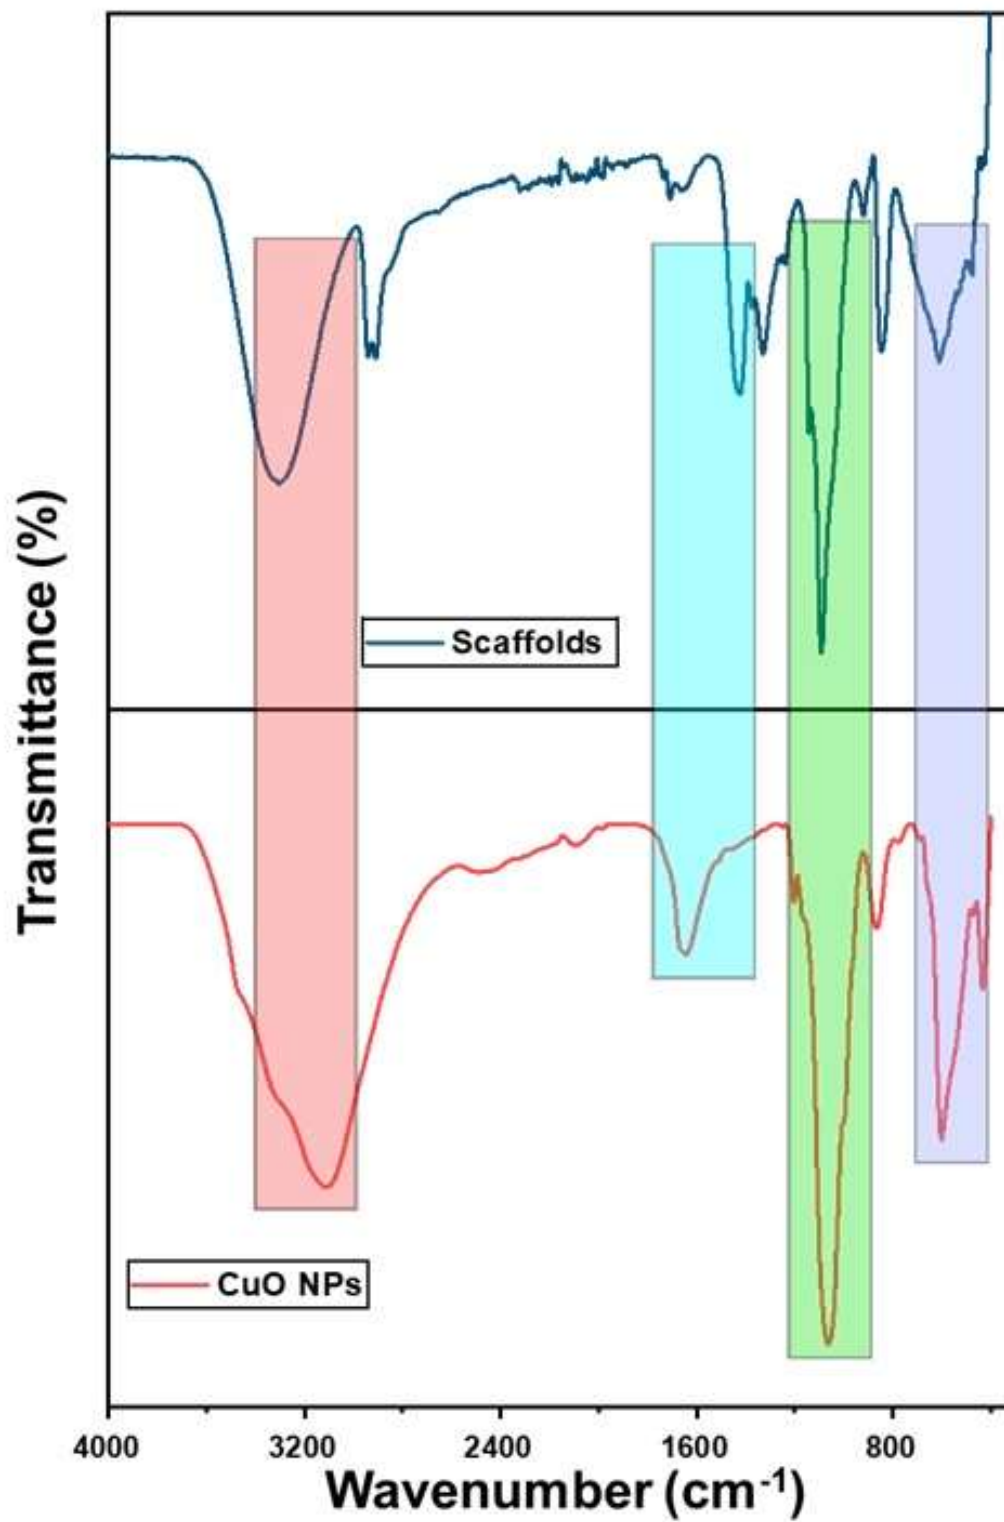


Fig. 2. FTIR spectra of CuO NPs and their incorporation into nanoscaffolds.

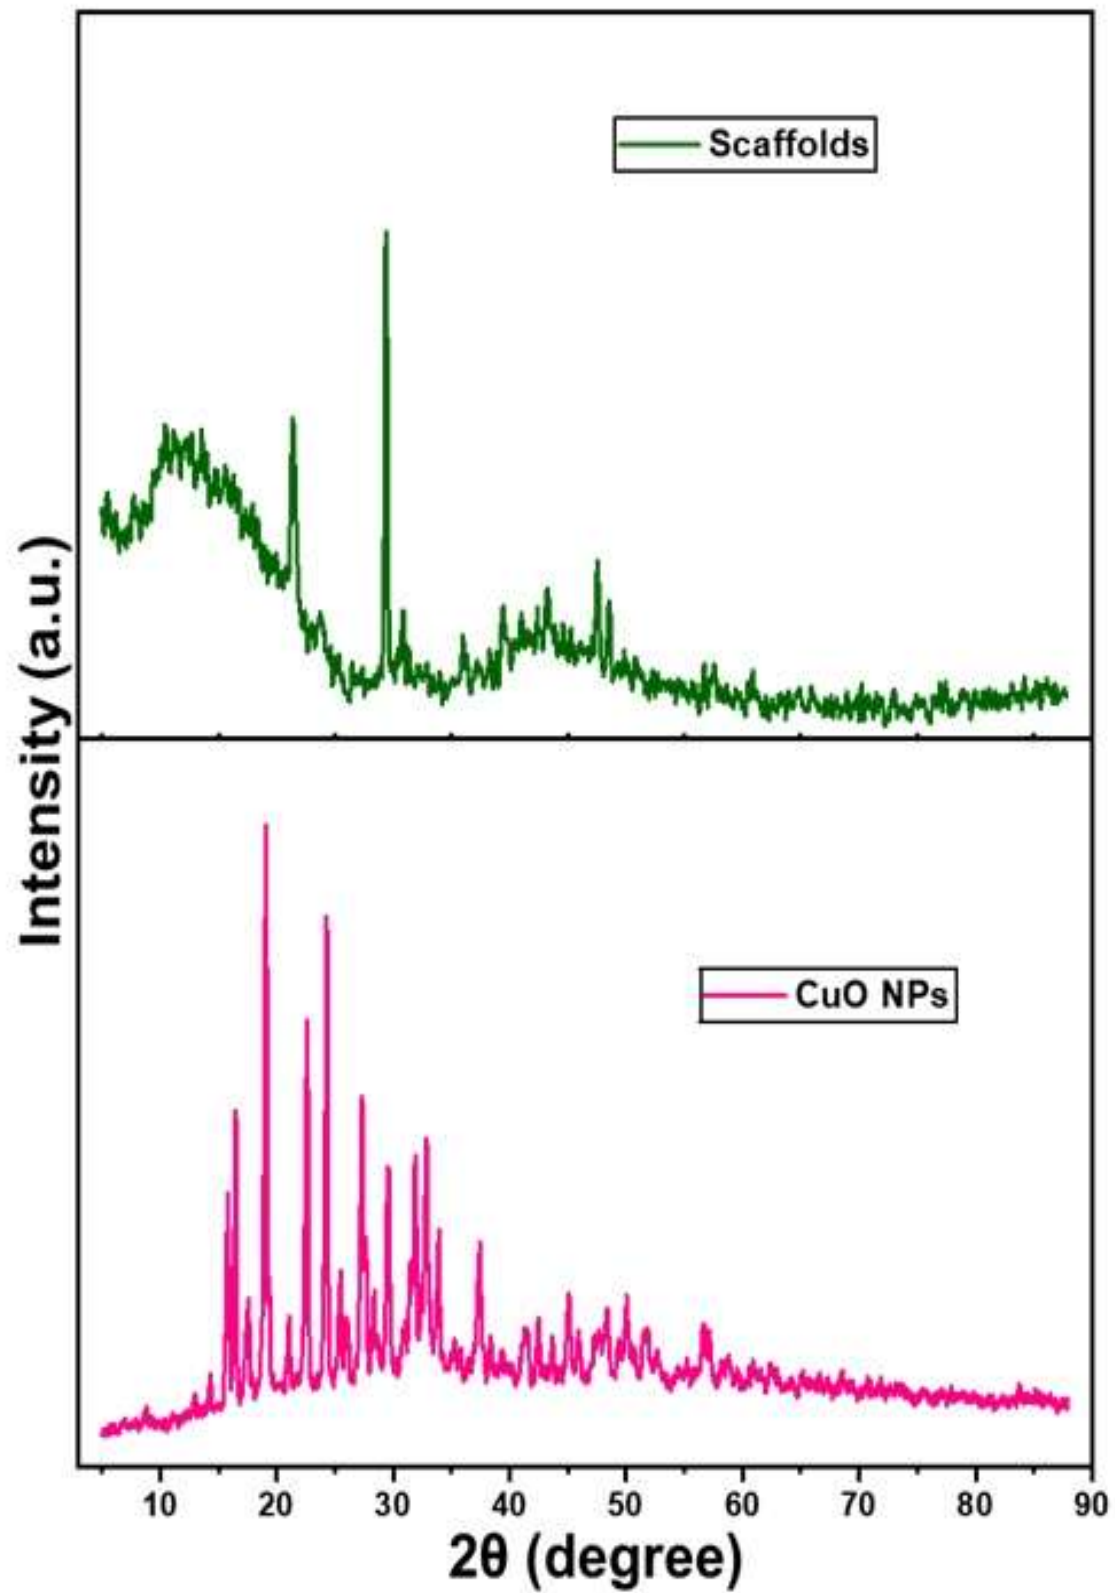


Fig. 3. XRD patterns of synthesized CuO NPs and CuO-loaded scaffolds.

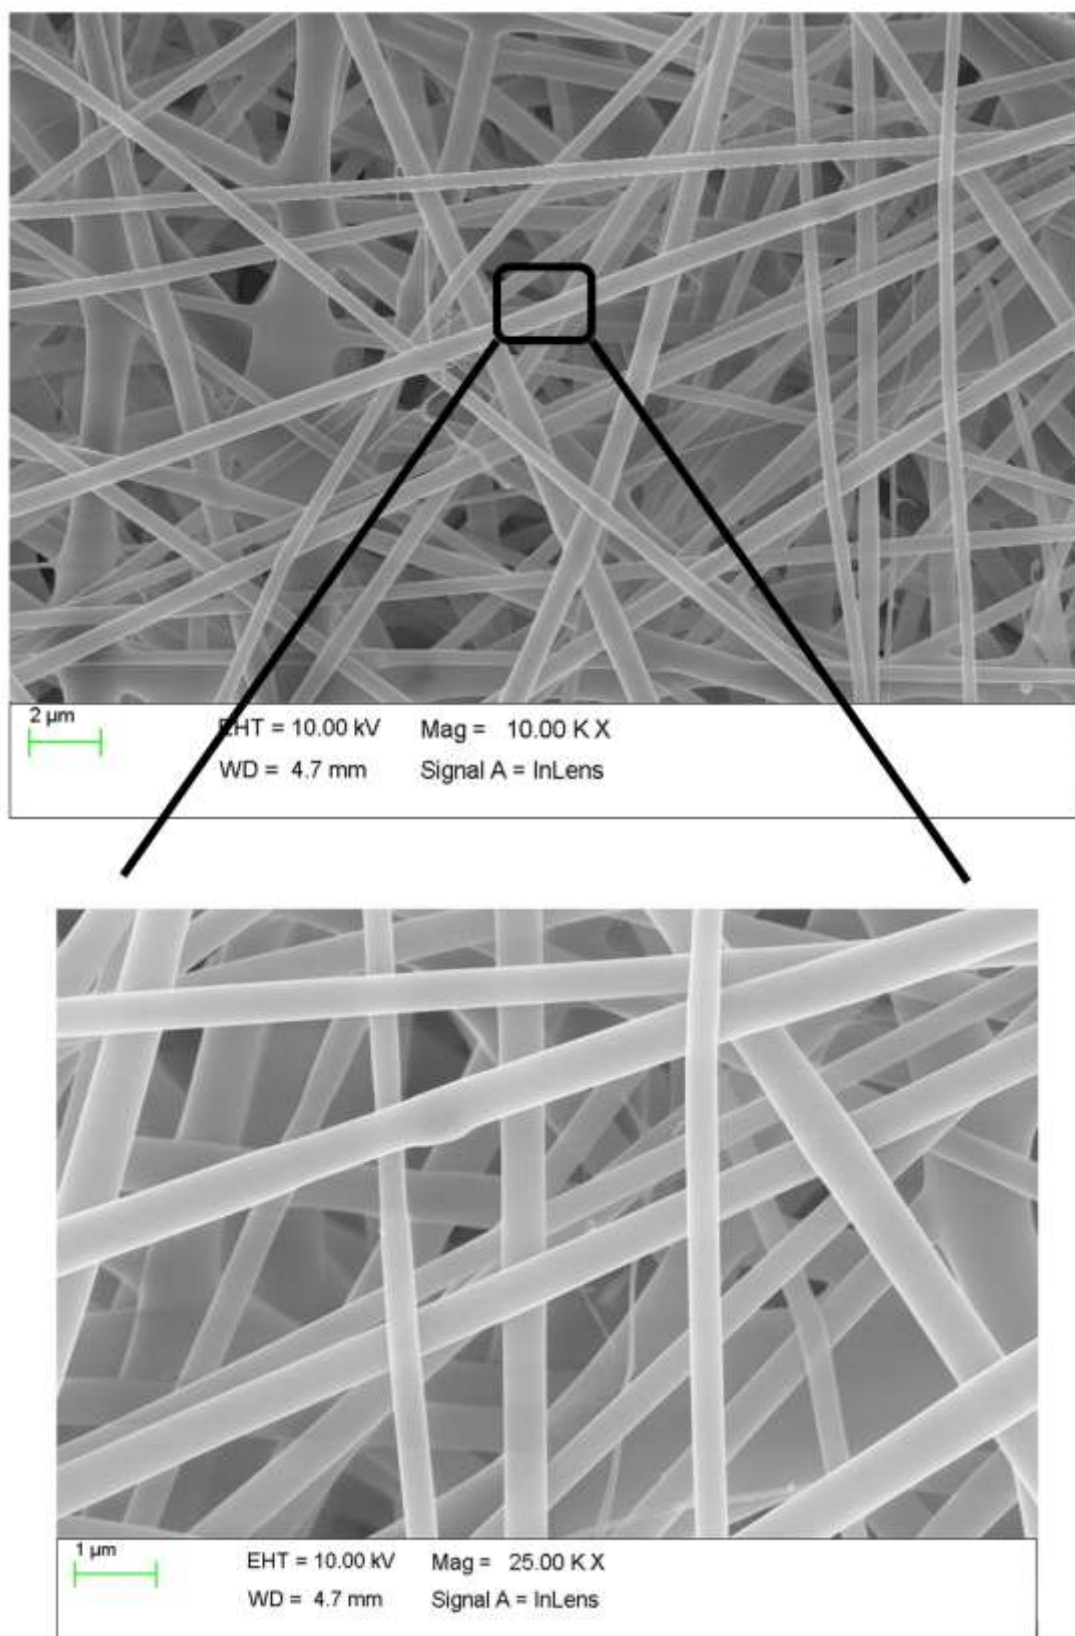


Fig. 4. SEM analysis of synthesized CuO NPs and CuO-loaded scaffolds

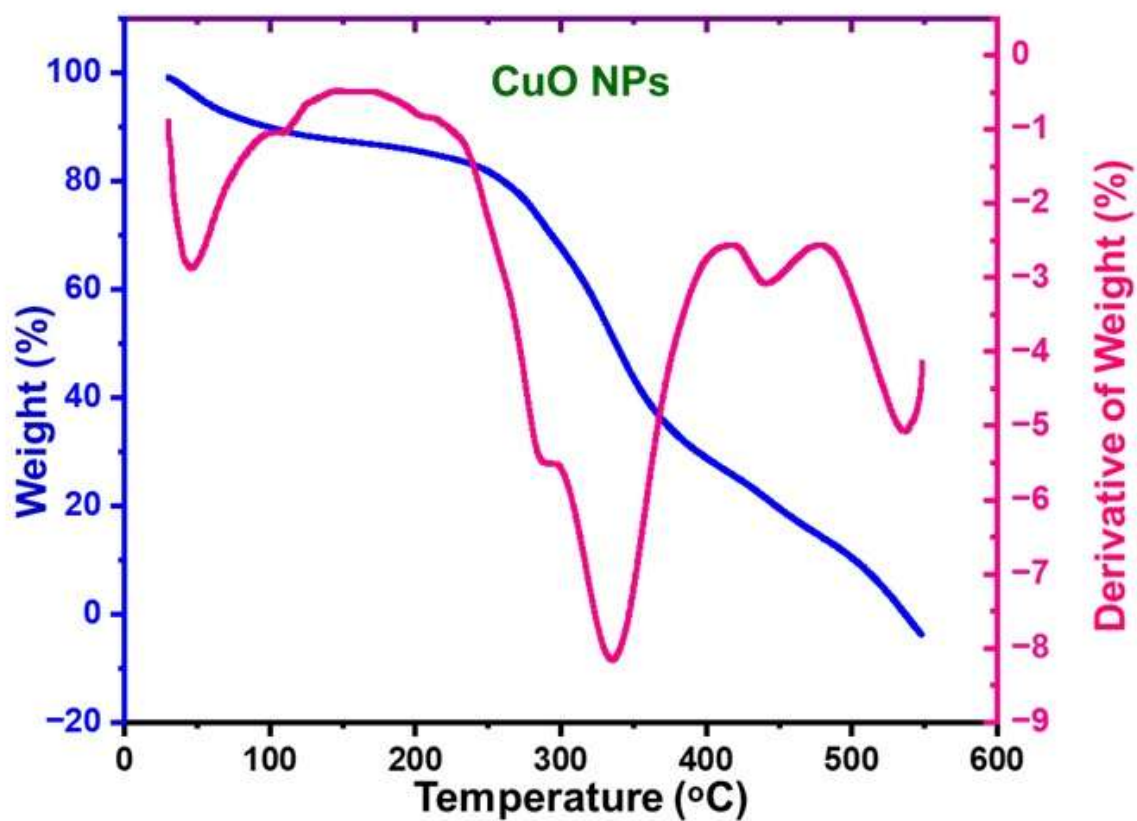


Fig. 5. Thermal degradation behavior of CuO-incorporated nanoscaffolds.

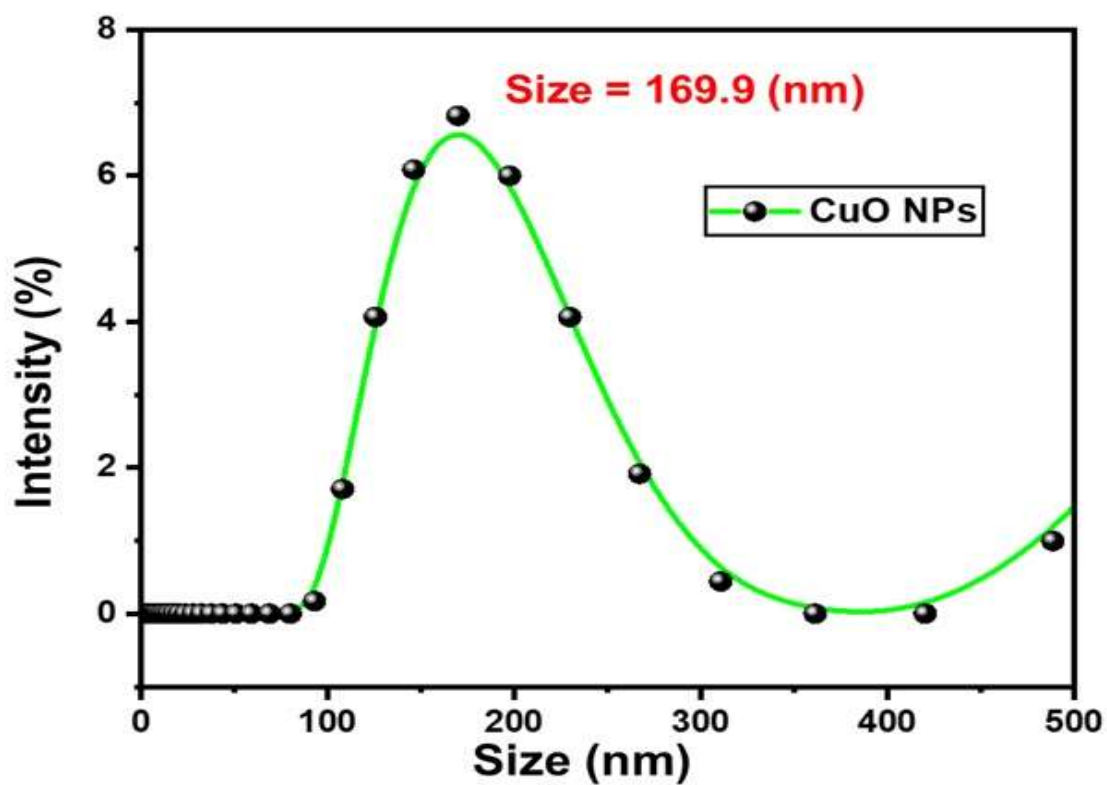


Fig.6. DLS particles size analysis of CuO NPs

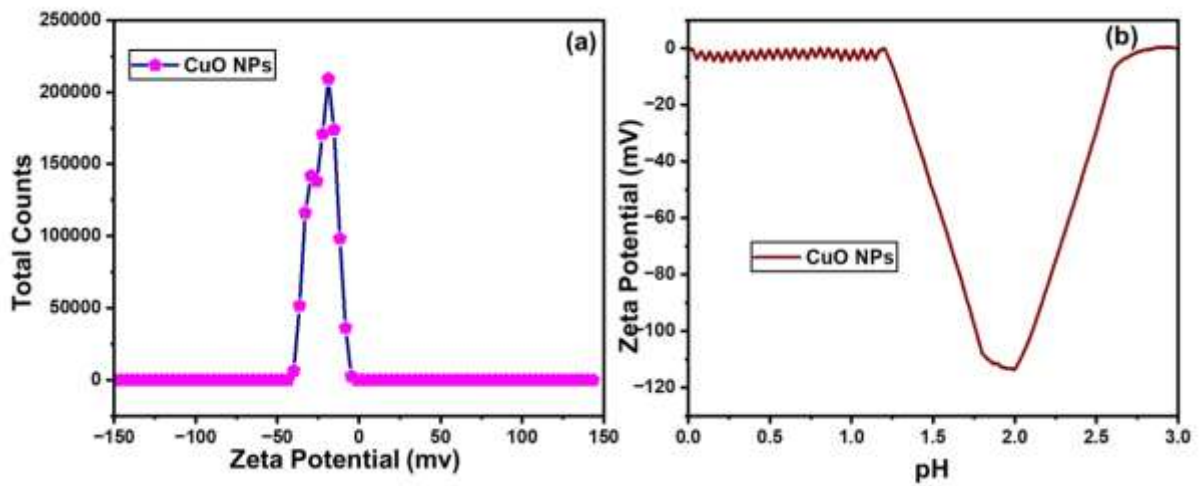


Fig.7. Zeta-potential analysis of CuO NPs

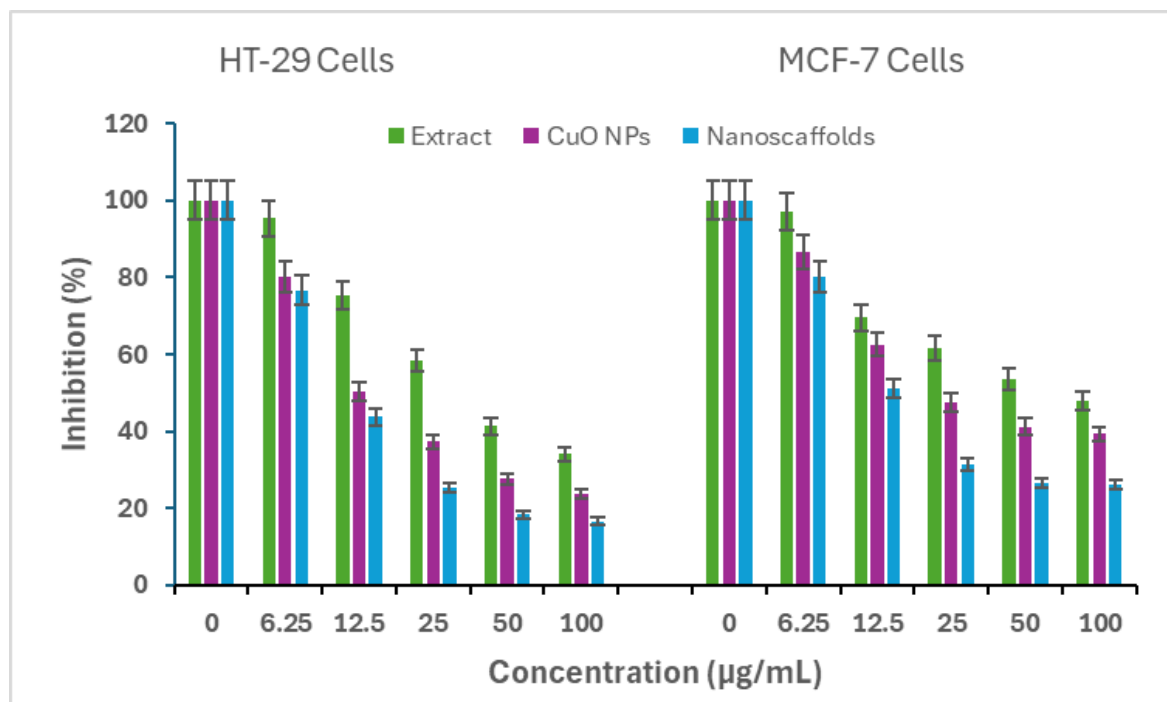


Fig. 8. Anticancer activity analysis of algal extract, CuO-NPs and starch/PVA/CuO-NPs nanoscaffolds